

Size Effects in Carbon Nanotubes

C.-H. Kiang,¹ M. Endo,² P. M. Ajayan,³ G. Dresselhaus,⁴ and M. S. Dresselhaus⁵

¹Department of Chemistry and Biochemistry, University of California, Los Angeles, California 90095

²Department of Electrical and Electronics Engineering, Faculty of Engineering, Shinshu University, Nagano 380, Japan

³Department of Materials Science and Engineering, Rensselaer Polytechnic Institute, Troy, New York 12180

⁴Francis Bitter Magnet Laboratory, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139

⁵Department of Electrical Engineering and Computer Science and Department of Physics,

Massachusetts Institute of Technology, Cambridge, Massachusetts 02139

(Received 21 May 1998)

The intershell spacing of multi-walled carbon nanotubes was determined by analyzing the high resolution transmission electron microscopy images of these nanotubes. For the nanotubes that were studied, the intershell spacing \hat{d}_{002} is found to range from 0.34 to 0.39 nm, increasing with decreasing tube diameter. A model based on the results from real space image analysis is used to explain the variation in intershell spacings obtained from reciprocal space periodicity analysis. The increase in intershell spacing with decreased nanotube diameter is attributed to the high curvature, resulting in an increased repulsive force, associated with the decreased diameter of the nanotube shells. [S0031-9007(98)06983-X]

PACS numbers: 61.46.+w, 81.10.Bk

The discovery of multi-walled carbon nanotubes [1] and single-walled carbon nanotubes [2,3] has prompted numerous studies of the structure, properties [4–8], and potential applications [9–11] of these exotic materials. For example, nanotubes are expected to have a high strength-to-weight ratio [11], which is advantageous in advanced composites to be used in high performance materials such as aircraft frames. The small dimension of the tubes shows promise for use as a gas absorption medium [12,13], a field emitter for use in flat-panel displays [14], and a nanoscale electronic device [15–18]. Most of the anticipated properties and applications are based on theoretical calculations for idealized tube structures [19–21]. A precise knowledge of the structure of real nanotubes and the interactions between them is essential for a reliable prediction of the potential applications.

Structural studies of carbon nanotubes have relied heavily on x-ray diffraction [22], scanning tunneling microscopy [23], and, predominately, high resolution transmission electron microscopy (HRTEM) and electron diffraction [1,24–26]. Carbon nanotubes are composed of concentric cylindrical graphene tubules, each with a structure similar to that of a rolled-up graphene sheet [4]. Iijima first showed with transmission electron microscopy that the intershell spacing of carbon nanotubes is about 0.34 nm [1], which was later confirmed by Zhang *et al.* with an electron diffraction study [24]. Saito *et al.* used powder X-ray diffraction to determine the lattice parameters of a bulk nanotube sample [22], and they concluded that the average intershell spacing is 0.344 nm. Bretz *et al.*, on the other hand, obtained a 0.375 nm spacing [27], and Sun *et al.* obtained a 0.36 nm spacing [28] by analyzing the HRTEM image of individual multiwalled nanotubes. These reports suggest a spread of intershell distances in carbon nanotubes, with a possible dependence on

the tube size. In the present work, we study the HRTEM nanotube images for several different multiwalled carbon nanotubes in an effort to understand the previously reported variation in the intershell spacing. To obtain quantitative results, we carried out a digital image analysis of HRTEM images, which allows us to relate the intershell spacings to the nanotube diameter and the number of shells in a given nanotube.

Carbon nanotube samples were prepared by the usual arc-discharge method [1,6]. The core of the deposit was crushed and dispersed in ethanol. A drop of this solution was transferred to a holey carbon microscope grid. HRTEM images were obtained with a TOPCON 002B microscope at 200 KV or a JEOL 4000 EX at 400 KV accelerating voltage. The images were scanned with a CCD camera and stored in a 1024 × 1024 pixel array of 256 gray-scale levels.

We carried out high resolution image analysis of nanotubes in real space, which allows us to measure individual intershell spacings as a function of tube diameter. Each data point is obtained as an average over 5 measurements to reduce the error to 3%, as shown in Fig. 1. Our data for all tube diameters that were studied show that the intershell spacing (\hat{d}_{002}) ranges from 0.34 to 0.39 nm, and that \hat{d}_{002} increases as the tube diameter decreases. The empirical equation for the best fit to the data is

$$\hat{d}_{002} = 0.344 + 0.1e^{-D/2} \quad \text{for } D \geq 0, \quad (1)$$

where D is the inner tube diameter, and all the constants are in nm. Equation (1) was obtained by a least-squares fit of the function $\hat{d}_{002} = A + B * e^{-C*D}$ to our experimental data (where A , B , and C are adjustable parameters), as depicted by the solid curve in Fig. 2. The intershell spacing decreases exponentially and approaches 0.344 nm as the tube diameter increases.

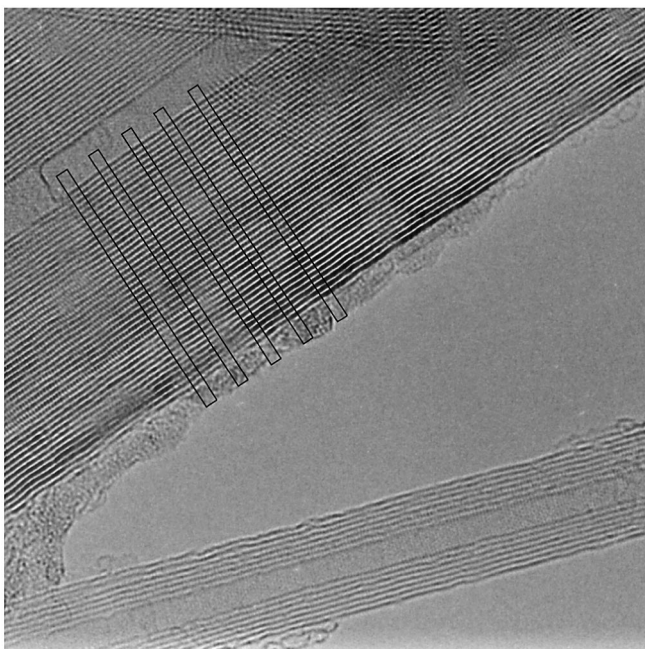


FIG. 1. HRTEM images of multi-walled carbon nanotubes. The intershell spacing \hat{d}_{002} was measured in the real space images, as indicated by the boxes.

For small tube diameters ($D < 10$ nm), an increase in the \hat{d}_{002} spacing with decreasing tube diameter is physically reasonable, since the repulsive forces of the graphene basal planes between adjacent tubes are larger for smaller diameter tubes, owing to their larger curvature, which perturbs the geometric and electronic structures relative to a planar graphene sheet. It has been pointed out that the HRTEM projected images of small diameter carbon nanotubes is asymmetric [29], but this effect on the measured intershell spacing is small and is within our experimental error. From Eq. (1) we estimated that the \hat{d}_{002} spacing is 0.41 nm for a 0.7 nm diameter tube, the smallest diameter carbon nanotube observed experimentally [30]. Furthermore, for finite sized tubes, the allowed diameters are discrete, which poses constraints on the intershell spacings. We calculated the distribution of allowed tube

$$\hat{d}_{002} = \sqrt{R(R + d_{002})} - \sqrt{R(R - d_{002})} \sim d_{002} + \frac{d_{002}^3}{8R^2} + O\left(\frac{1}{R^3}\right) \text{ as } R \rightarrow \infty, \quad (3)$$

where $R = D/2$ is the tube radius and d_{002} is 0.344 nm, the asymptotic limit of the \hat{d}_{002} spacing.

The asymptotic limit deduced by Eq. (1) is 0.344 nm, the same spacing as that in a turbostratic graphite. This is expected since defect-free multi-walled nanotubes have circular cross sections. In any single multi-walled nanotube, the diameter of each constituent graphene shell is different, which prevents perfectly correlated graphitic stacking. Some of the fluctuations in the spacings may be associated with the jumps in spacing at points where the helix angle changes [31]. A \hat{d}_{002} value smaller than that of a turbostratic graphite, however, may occur when

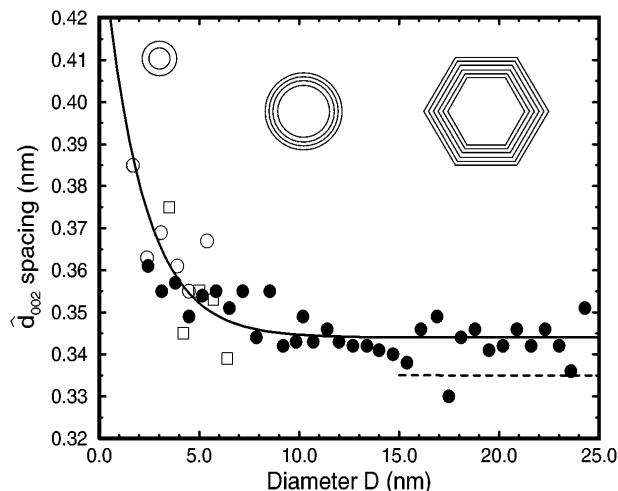


FIG. 2. The spacing \hat{d}_{002} decreases as the tube diameter increases, and approaches 0.344 nm at roughly $D = 10$ nm. The data were measured from three different nanotubes indicated by different symbols. Hollow circles: from a 7-shell tube with innermost diameter $D_{\min} = 1.7$ nm (shown in Fig. 1); solid circles: from a 41-shell tube with $D_{\min} = 2.6$ nm (shown in Fig. 1); hollow squares: from a 6-shell tube with $D_{\min} = 3.5$ nm (from Ref. [28], not shown). The curve $\hat{d}_{002} = 0.344 + 0.1e^{-D/2}$ is the least-squares fit to the experimental data (see text). For small tube diameters, the \hat{d}_{002} spacing increases exponentially as D decreases. For intermediate tube diameters, the \hat{d}_{002} spacing is a slowly varying function of D . For large D , graphitization may occur resulting in a polygonal cross section. The dashed line indicates the expected decrease in \hat{d}_{002} owing to the local graphitic stacking.

diameters D with different helicities given by

$$D(\text{nm}) = \frac{\sqrt{3} \times 0.142}{\pi} \sqrt{m^2 + mn + n^2}, \quad (2)$$

where m and n are integers. A discontinuity of 0.01 nm occurs for very small diameter nanotubes ($D < 3$ nm). This geometric effect may explain the deviation of \hat{d}_{002} values from the predicted curve shown in Fig. 2.

For large tube diameters ($D > 10$ nm), the variation in \hat{d}_{002} spacing can be explained by assuming a uniform charge density

the energy gained by the local graphitic stacking is less than the energy introduced by the defects associated with the stacking. Intershell spacings smaller than 0.344 nm, resulting from a polygonal cross section, have frequently been observed for large diameter nanotubes [32,33] and for vapor-grown carbon fibers [34].

We also measured the lattice constants in reciprocal space, which complement the results obtained from real space images. With a known minimum diameter of a nanotube (measured directly from the HRTEM images), we calculated the diffracted spot positions from a crystal with a slowly varying c unit cell length defined by Eq. (1). The

calculated results were then compared to the experimental data. Figure 3a presents data for a nanotube with the 0.213 nm d_{100} lattice fringes of the graphite basal plane clearly resolved, and the corresponding FFT is shown in Fig. 3b. The intershell spacings (\hat{d}_{002}) were deduced from the power spectra, using the location of the highest intensity as the spot position, as shown in Fig. 3b.

We used the 0.213 nm spacing between $\{100\}$ fringes as a calibration standard, based on the X-ray diffraction study [22] showing that the C-C bond lengths in the nanotubes are the same for both graphite and carbon nanotubes (0.142 nm) [22]. The tube diameters, defined as the average diameter (D_a) of the tubes used for the FFT, were obtained from the real space images.

In reciprocal space, the scattering amplitude $F(k)$ is

$$F(k) = \sum_n f(k) e^{-i\mathbf{k}\cdot\mathbf{r}_n}, \quad (4)$$

where n is the n th unit cell in the crystal, \mathbf{k} is the reciprocal lattice vector, \mathbf{r} is the atomic position in real space, and $f(k)$ is proportional to the atomic form factor for electron scattering of carbon and is a slow varying function of k for electron scattering. Since we were interested only in diffraction along the (002) direction, we constructed a crystal of parallel graphene sheets with varying intershell distances, as depicted in Fig. 4a. Defining z to be perpendicular to the graphene planes, we can express z as a function of the cell n (for $n \geq 2$):

$$z_n = z_{n-1} + \hat{d}_{002, n-1}, \quad (5)$$

where z_n is the atomic position of the n th unit cell along the z axis relative to the origin, \hat{d}_{002} is evaluated with Eq. (1), and $z_1 = R_{\min}$ is the minimum radius of the nanotubes. The scattering amplitude F for the crystal shown in Fig. 4a is

$$F = f \sum_{n=1}^N e^{-ik_z z_n}, \quad (6)$$

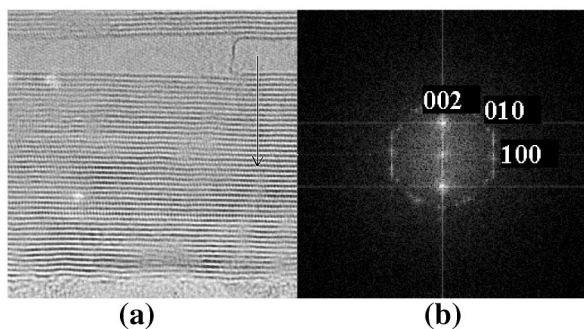


FIG. 3. (a) Digitized HRTEM of the core region of the top carbon nanotube shown in Fig. 1, where the $\{100\}$ lattice fringes are clearly resolved. The average diameter is illustrated in this micrograph. (b) Fast Fourier transform (FFT) of the nanotube. The (002), (100), and (010) reflections are resolved. The position of the spots is measured at the location of the highest intensity. The d_{100} spacing (0.213 nm) is used as a calibration standard.

where N is the total number of unit cells along the z axis. Thus the diffracted intensity I is

$$I = |F|^2 = f^2 \left[\left(\sum_{n=1}^N \cos(k_z z_n) \right)^2 + \left(\sum_{n=1}^N \sin(k_z z_n) \right)^2 \right]. \quad (7)$$

For a crystal with a constant \hat{d}_{002} , Eq. (7) can be evaluated analytically, and the peak position (defined as the intensity maximum of the peak) is at $2\pi/\hat{d}_{002}$. For a crystal with a slowly varying $\hat{d}_{002, n} = d_{002} + \delta d(n)$ for all tubes, the peak is shifted relative to the k_z value for d_{002} . Using this model, we evaluated numerically the \hat{d}_{002} spacing as a function of the average tube diameter (D_a), starting with the smallest possible D_a value which can occur for a given n , where n is the number of shells in a nanotube. By knowing the number of shells and the average diameter of a nanotube, we can predict the (002) spot position in Fourier space. The resulting curves for $n = 2, 5, 10$, and 40 are shown in Fig. 4b. The data from the Fourier analysis of the three tubes surveyed in Fig. 2 (where $n = 6, 7$, and 41) agree with our model, supporting

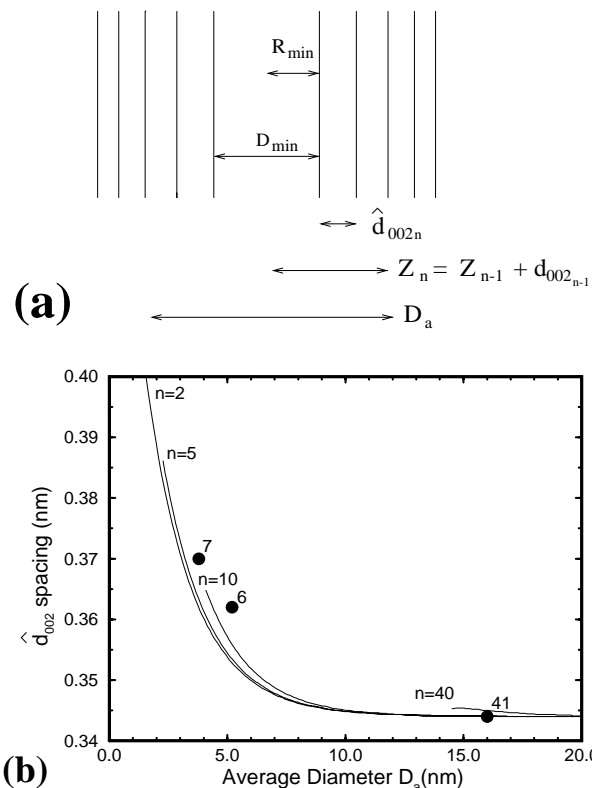


FIG. 4. (a) Model for a nanotube crystal with a varying intershell spacing. The \hat{d}_{002} as an exponential function of tube diameter is defined in Eq. (1). (b) The intershell spacing \hat{d}_{002} as a function of the average tube diameter (D_a), where n is the number of shells in a nanotube. The curves are calculated for $n = 2, 5, 10$, and 40, using the above model and Eq. (1). The three data points (with 2% error) shown by the large full circles were obtained from the power spectra of the two tubes surveyed in Fig. 1 and the tube in Ref. [28].

our conclusion that the intershell spacing is a function of tube diameter.

We also found that the nanotubes with smaller innermost tube diameters often have fewer shells. This may be because the kinetics of the growth reaction is correlated with the product stability. According to the multi-walled nanotube growth mechanism [7,35], nanotubes grow by first forming a nucleating shell, followed by epitaxial growth of additional shells. Larger intershell spacings resulting from a higher strain energy of the nanotubes decreases the stability of the nanotube. Because of the larger intershell spacings and lower stability of small diameter tubules, the epitaxial growth of additional shells onto the nucleating core is slower for smaller diameter tubes in comparison with larger diameter tubes. Therefore, the radial growth rate of nanotubes is also expected to be related to the nucleating tube diameter.

The small number of shells n may also contribute to the size effect that causes increased intershell spacing. This effect, however, is expected to be smaller compared to the diameter effect. According to the shell-by-shell growth model, a variation of the intershell spacing as a function of n requires a change in the intershell spacing as the number of shells increases, which would result in a decrease in C-C bond length. For example, a spacing that changes from 0.37 to 0.35 nm will result in a 5% decrease in bond length, which implies reducing the C-C bond length from 0.142 to 0.134 nm, a nearly impossible process. Our experimental results can be explained solely by the diameter size effect, which suggests that the effect due to a small number of carbon shells is within the experimental uncertainties. Incorporation of the n effect may, however, provide further refinement to our model.

In summary, we have studied the nanotube structures by high resolution transmission electron microscopy and digital image analysis. We found that the intershell spacing of nanotubes decreases with increasing tube diameter, approaching 0.344 nm asymptotically at a tube diameter of roughly 10 nm. The size effect is more profound in the small diameter ($D < 10$ nm) region, where each additional shell results in a measurably different \hat{d}_{002} spacing. The physical and chemical properties may also vary owing to the change in intershell spacing of the nanotubes. For example, nanotubes of larger intershell spacing should be less stable and, therefore, more reactive. The variation in interaction forces of small diameter nanotubes should modify single-walled carbon nanotube surface properties, which may result in useful characteristics for storage media such as hydrogen fuel cells and batteries.

We thank Dr. S. Iijima for helpful discussions. C. H. K. and P. M. A. acknowledge the financial support from the UC Energy Institute and the Alexander von Humboldt Foundation, respectively. Part of the work by M. E. is supported by the Ministry of Education, Science and

Culture, Japan. The work at MIT is supported by NSF Grant No. DMR-95-10093.

- [1] S. Iijima, *Nature (London)* **354**, 56 (1991).
- [2] S. Iijima and T. Ichihashi, *Nature (London)* **363**, 603 (1993).
- [3] D. S. Bethune *et al.*, *Nature (London)* **363**, 605 (1993).
- [4] M. S. Dresselhaus, G. Dresselhaus, and R. Saito, *Carbon* **33**, 883 (1995).
- [5] J. W. Mintmire and C. White, *Carbon* **33**, 893 (1995).
- [6] T. W. Ebbesen and P. M. Ajayan, *Nature (London)* **358**, 220 (1992).
- [7] M. Endo and H. W. Kroto, *J. Phys. Chem.* **96**, 6941 (1992).
- [8] N. G. Chopra *et al.*, *Nature (London)* **377**, 135 (1995).
- [9] P. M. Ajayan and S. Iijima, *Nature (London)* **361**, 333 (1993).
- [10] A. G. Rinzler *et al.*, *Science* **269**, 1550 (1995).
- [11] R. S. Ruoff and D. C. Lorents, *Carbon* **33**, 925 (1995).
- [12] M. W. Maddox and K. E. Gubbins, *Langmuir* **11**, 3988 (1995).
- [13] A. C. Dillon *et al.*, *Nature (London)* **386**, 377 (1997).
- [14] W. A. de Heer, A. Châtelain, and D. Ugarte, *Science* **270**, 1179 (1995).
- [15] L. Chico *et al.*, *Phys. Rev. Lett.* **76**, 971 (1996).
- [16] M. Menon and D. Srivastava, *Phys. Rev. Lett.* **79**, 4453 (1997).
- [17] T. W. Odom, J.-L. Huang, P. Kim, and C. M. Lieber, *Nature (London)* **391**, 62 (1998).
- [18] J. W. G. Wildoer *et al.*, *Nature (London)* **391**, 59 (1998).
- [19] N. Hamada, S. Sawada, and A. Oshiyama, *Phys. Rev. Lett.* **68**, 1579 (1992).
- [20] M. R. Pederson and J. Q. Broughton, *Phys. Rev. Lett.* **69**, 2689 (1992).
- [21] K. Akagi *et al.*, *Phys. Rev. Lett.* **74**, 2307 (1995).
- [22] Y. Saito *et al.*, *Phys. Rev. B* **48**, 1907 (1993).
- [23] M. Ge and K. Sattler, *Science* **260**, 515 (1993).
- [24] X. F. Zhang *et al.*, *J. Cryst. Growth* **130**, 368 (1993).
- [25] *High-Resolution Transmission Electron Microscopy and Associated Techniques*, edited by P. R. Buseck, J. M. Cowley, and L. Eyring (Oxford University Press, New York, 1988).
- [26] C.-H. Kiang *et al.*, *J. Phys. Chem.* **98**, 6612 (1994).
- [27] M. Bretz, B. G. Demczyk, and L. Zhang, *J. Cryst. Growth* **141**, 304 (1994).
- [28] X. Sun *et al.*, *Phys. Rev. B* **54**, R12629 (1996).
- [29] J. M. Cowley and S. D. Packard, *Ultramicroscopy* **63**, 39 (1996).
- [30] C.-H. Kiang and W. A. Goddard III, *Phys. Rev. Lett.* **76**, 2515 (1996).
- [31] M. Liu and J. M. Cowley, *Carbon* **32**, 393 (1994).
- [32] M. Liu and J. M. Cowley, *Ultramicroscopy* **53**, 333 (1994).
- [33] T. W. Ebbesen, *Annu. Rev. Mater. Sci.* **24**, 235 (1994).
- [34] J. S. Speck, M. Endo, and M. S. Dresselhaus, *J. Cryst. Growth* **94**, 834 (1989).
- [35] S. Iijima, P. M. Ajayan, and T. Ichihashi, *Phys. Rev. Lett.* **69**, 3100 (1992).